

This item was submitted to [Loughborough's Research Repository](#) by the author.
Items in Figshare are protected by copyright, with all rights reserved, unless otherwise indicated.

Innovative technologies for sustainable textile coloration, patterning, and surface effects

PLEASE CITE THE PUBLISHED VERSION

https://doi.org/10.1007/978-3-030-38545-3_4

PUBLISHER

Springer, Cham

VERSION

AM (Accepted Manuscript)

PUBLISHER STATEMENT

This book was accepted for publication in Muthu S., Gardetti M. (eds) Sustainability in the Textile and Apparel Industries. Sustainable Textiles: Production, Processing, Manufacturing & Chemistry. The final published version can be found here: https://doi.org/10.1007/978-3-030-38545-3_4

LICENCE

CC BY-NC-ND 4.0

REPOSITORY RECORD

Kane, Faith, Jinsong Shen, Laura Morgan, Chetna Prajapati, John Tyrer, and Edward Smith. 2020. "Innovative Technologies for Sustainable Textile Coloration, Patterning, and Surface Effects". Loughborough University. <https://hdl.handle.net/2134/12323465.v1>.

Innovative Technologies for Sustainable Textile Colouration, Patterning and Surface Effects

Faith Kane ¹, Jinsong Shen ², Laura Morgan ³, Chetna Prajapati ⁴, John Tyrer ⁴, Edward Smith ²

¹ Massey University, Wellington, New Zealand ² De Montfort University, Leicester, UK ³ University of the West of England, Bristol, UK ⁴ Loughborough University, Loughborough, UK

Abstract

The environmental impact of textile dyeing and finishing is of paramount concern in the textile industry. Enzyme and laser processing technologies present attractive alternatives to conventional textile colouration and surface patterning methods. Both technologies have the capability to reduce the impact of manufacturing on the environment by reducing the consumption of chemicals, water and energy, and the subsequent generation of waste. Two emerging textile processing technologies, laser processing and enzyme biotechnology were investigated as a means of applying surface design and colour to materials with a focus on improving the efficiency and sustainability of existing textile design and finishing methods.

Through industrial stakeholder engagement and interdisciplinary research involving textile design, fibre and dye chemistry, biotechnology and optical engineering, this design-led project brought together design practice and science with a commercial focus. Each technology was used to modify targeted material properties, finding and exploiting opportunities for the design and finishing of textiles. The work resulted in a catalogue of new colouration and design techniques for both technologies making it possible to achieve: selective surface pattern by differential dyeing, combined three-dimensional and colour finishing and novel colouration of textile materials.

The chapter provides a literature review mapping the use of enzyme biotechnology and laser processing technology within textile design and manufacturing to date, identifying current and future opportunities to reduce environmental impacts through their application. The methodological approach, which was interdisciplinary and design-led, will be introduced and the specific design and scientific methods applied will be detailed. Each of the techniques developed will be discussed and examples of the design effects achieved will be presented. And, an indication of the reductions in chemical effluent efficiencies in resource use, and design flexibility in comparison with traditional textile colouration and surface patterning techniques will be given.

Keywords

Textile colouration, laser processing, enzyme processing, agile manufacturing, sustainable design, material finishing, textile design

1 Introduction

Colour, pattern, and surface effects are fundamental elements of textile design and production, and critical to the functional and expressive role they play in material culture. Dyeing, printing, and finishing processes offer extensive opportunities for creativity and innovation within this area, but in the context of globalized mass production, they have become one of the most environmentally damaging facets of the textile industry. Due to the scale of the industry, the environmental and social impacts are significant and have been identified as one of the key challenges to achieve sustainability within the sector. Traditional methods routinely involve harmful chemicals that can have devastating

effects on workers' health and the local environment through exposure and water and air pollution. In addition, vast amounts of water and energy are consumed during processing, leaving large water footprints in the developing economies where much industrial activity currently occurs, adding to the decline of water tables, reducing sources of clean water, and increasing associated costs [77].

In response to this, advances in technology are emerging that facilitate new methods of textile colouration, pattern, and surface effects with promising signs for more environmentally friendly processing [42]. Methods such as plasma processing, supercritical carbon dioxide dyeing, ultrasonic dyeing, and digital printing have begun to be adopted within various industrial contexts. Plasma treatment, for example, aids more efficient dyeing through facilitating increased dyeing rates, dye-bath exhaustion, and improved dye homogeneity on all fibre types [37]. Supercritical carbon dioxide dyeing, adopted for some product ranges by brands such as Nike and Adidas, claims waterless processing without effluent production, resulting in high dye fixation and good leveling on polyester with potential for application to a wider range of substrates [8, 17]. Within the context of circular design and manufacturing, ultrasonic dyeing has been implemented to enable natural dye solutions for natural and regenerated fibre by IndiDye®. Within this process, ultrasonic pressure waves push the dye into the core of the fibre eliminating the need for chemical fixatives, auxiliaries, and wastewater [26]. And, digital printing methods have enabled more bespoke and on-demand modes of textile colouration, pattern, and surface design through platforms such as Spoonflower, which have the potential to minimize surplus stock and pre-consumer waste [84].

Alongside these approaches, enzyme and laser processing technologies present attractive alternatives to conventional methods of producing colour, pattern, and surface effects and have the capability to minimize the impact of manufacturing on the environment through increasing efficiency and reducing the consumption of chemicals, water, and energy. This presents opportunities for sustainable innovation through the redesign and modification of existing products and systems. Further, both technologies have the potential to catalyse and facilitate new post-industrial systems of production and consumption through opportunities for open and codesign, agile, and responsive manufacturing.

1.1 Overview

This chapter provides a summary of research undertaken to investigate laser processing and enzyme biotechnology as a means of applying colour, pattern, and surface effects to textiles with a focus on providing more efficient alternatives to traditional techniques. Through industrial stakeholder engagement and interdisciplinary research involving textile design, fibre and dye chemistry, biotechnology, and optical engineering, this textile-led project brought together design practice and science with a commercial focus. Each technology was used to modify targeted material properties, finding and exploiting opportunities for the design, and finishing of textiles. The work resulted in a catalogue of new colouration and design techniques for both technologies.

This chapter provides overviews of the use of laser processing and enzyme biotechnology within textile design and manufacturing to date, identifying current and future opportunities to reduce environmental impacts through their application. First, the methodological approach, which was interdisciplinary and design-led, will be introduced. Each of the techniques developed during the work will be discussed, and examples of the design effects achieved will be presented. Finally, an indication of the reductions in chemical effluent, efficiencies in resource use, and design flexibility in comparison with traditional textile colouration and surface patterning techniques will be given.

1.2 Methodology

The work undertaken employed a textile-led interdisciplinary methodology, drawing on methods associated with design, craft, and engineering. These disciplines find a natural meeting point within textile practice, which tacitly draws on knowledge from each [68]. While it has been noted that engineers and designers rarely meet within commercial settings [52], the need for interdisciplinarity within research and innovation has grown in response to the complexity of current societal challenges [19, 25, 53]. Within this context, textile design research methodologies have evolved over recent decades to construct bridges between concepts of beauty and utility, aesthetics, and function, which enable the investigation of the imaginative alongside the technical (Philpott 2012), and more latterly toward notions of “quantified design” [25].

The research outlined in this chapter is aligned with such thinking, employing methods originating in design practice and craft, alongside scientific experiment in a unified approach. This was underpinned by the establishment of a team of researchers with backgrounds in design, textile chemistry and biotechnology, and optical engineering. Distinct but aligned periods of creative exploration and scientific experiment were undertaken and synthesized through design practice [51, 52, 70]. This generated both qualitative and quantitative data, which was analysed to understand: the creative potential of the techniques established; the properties and qualities of resulting textiles as relevant to industry; and the potential savings in chemical, water, and energy use. The aim is to investigate the creative potential of laser and enzyme processing as more sustainable alternatives to traditional methods of achieving textile colouration, pattern, and surface effects. As such, the work progressed to establish workshop conditions for textile sampling using both laser and enzyme processing; develop new techniques for colouration, patterning, and surface effects; and create textile design collections for analysis, review, and evaluation. The following text provides further detail relating to the methods employed in regard to both the laser and enzyme investigations, respectively.

2 Laser Processing

A laser is a device that emits an intense beam of light composed of electromagnetic waves that are in phase (coherent) and of the same wavelength (monochromatic). Infrared and ultraviolet laser irradiation can be harnessed for photothermal and photochemical properties, respectively. Lasers are used widely in manufacturing for materials processing, including cutting, marking, welding, and drilling, as well as for medical procedures and measurement applications [10]. The use of laser technology for textile processing is less established. However, as research develops and the cost of machinery becomes more affordable for factories and educational institutions, their use has become more widespread [30].

Lasers provide an energy efficient means of material processing and have been shown to have fibre modification capabilities that can enhance and improve dyeability without excessive water or chemicals, therefore offering potential environmental benefits compared to traditional textile dyeing processes. For graphic processing, they enable specificity and control by digital generation of imagery. The effect of laser irradiation on different textile substrates varies depending on the method of application and the material. Laser technology’s advantages of digital control for design flexibility and precision capabilities coupled with noncontact processing offer unique benefits not achievable by other means. It is these unique attributes and controllable parameters of the laser that offer potential for novelty and innovation through consideration of new processes and opportunities for textile design.

For the design of textiles, laser processing has been utilized across the fashion, accessory, and home textile market sectors. Couture and high street clothing sectors have embraced laser technology to create fashion-led effects, such as fringing, and as a form of garment embellishment. Offering precision cutwork with heat sealing of fabric edges to prevent fraying, laser cutting technology has become standard equipment in university art and design departments, leading to a growth in creative use within textile design. For example, Hur [32] used the laser to cut individual textile units to build customizable, modular fabrics, while Moriarty's [58] layered laser cut rubber "lace" gave a new aesthetic to the traditional textile process of lace making.

While laser technology excels in providing efficient, noncontact cutting, it can also be harnessed for the purpose of textile surface modification. Lasers have been used to replace chemical and wet processing techniques to recreate conventional textile surface design effects such as devoré and stonewashed denim. Infrared CO₂ laser technology has been adopted successfully for commercial processing of denim in the manufacture of worn or weathered-look jeans. Through precise parameter control, infrared laser irradiation can fade the colour of indigo-dyed denim by removing a thin layer of dye from the surface of the cotton, revealing the white undyed fibre underneath [38, 62, 63]. In comparison to traditional stone washing processes, the technique has eliminated the use of chemicals and reduced water use by 85% saving significant wastewater effluent (Costin et al. 1999). This has led to the development of garment and textile-specific laser machinery. For example, Jeanologia [34] produced laser processing equipment capable of processing fabric lengths and direct-to-garment (DTG) laser finishing equipment that allows the garment to be processed in three-dimensional form.

Advantages of utilizing infrared laser irradiation as an efficient, dry, and targeted heat source provide positive implications for reduction of wastewater and processing time of textile production in comparison to traditional wet finishing methods. These advantages have been beneficial to denim manufacture in creating laser-faded effects on denim [18, 63]. As such, use of CO₂ laser technology has become increasingly commonplace in the textile industry [62]. The use of laser technology on other textile substrates presents numerous further opportunities for sustainability in the field of textile research (Allwood et al. 2006). This section reviews emerging laser-based techniques for textile colouration and surface patterning by utilizing laser irradiation for fibre modification, dye fixation, or thermal setting.

2.1 Laser Colouration and Surface Patterning: Fibre Modification

Research studies have reported harnessing the photochemical and photothermal energy that laser processing can provide to modify textile material properties. Studies that have examined the effect of laser irradiation on the properties of synthetic fibres and fabrics using ultraviolet (UV) (Bahners et al. 1993; [36, 88] and infrared (IR) [7, 49] irradiation have reported an increase in the dye absorption properties of synthetic polymers, resulting in improved dye performance. Laser enhanced dye uptake has been identified on PET (polyester) [3, 21, 36], polyamide (nylon) [9, 21], and polypropylene textiles [76]. Enhanced hydrophilic properties of polymer fibres after laser irradiation have been attributed to an increase in the amorphous: crystalline ratio [7, 49] that improves bonds between dyestuffs and polymer due to the creation of more functional groups after laser irradiation [7, 76]. Capacity for enhanced dyeing has also been attributed to morphological changes to polymer fibres [36], with surface roughness providing increased surface area for improved adhesion of dye particles to fibre [5, 6, 21, 76, 87].

Increasing the intensity of laser irradiation increased the colour strength of laser pre-treated synthetic fabrics after dyeing [40, 49, 76]. Therefore, by controlling the intensity of laser irradiation delivered to the substrate, the uptake of dye on the material could be controlled, allowing varied depth of shade

across the textile surface. High-intensity laser irradiation increased the wettability, light, rubbing, and wash fastness of tested fabrics; however, properties such as bending rigidity and tensile strength were negatively affected by an increase in laser intensity [31, 76].

On cotton, unlike synthetic fibres, laser modification was found to reduce the amount of direct dye absorbed, leading to decreased colour strength as laser intensity increased [15, 50].

Fewer studies have investigated the effect of laser irradiation on the properties of wool; however, a small number have shown that laser irradiation can reduce felting and shrinkage of woollen textiles [60] and that UV [67, 89] and IR [54] laser irradiation can improve the dyeability of wool. A combination of laser and plasma treatments was shown to increase hydrophilic properties as an all-over treatment on woollen textiles [20]. UV irradiation was found to disrupt the cysteine disulphide bonds on wool fibres and increase surface oxidation leading to a reduced water wetting time [75], suggesting that UV irradiation increased the hydrophilic properties of wool fibres.

The effects of laser irradiation on colouration for textiles have been studied from a design perspective, identifying the potential for surface pattern achieved through tonal dye differentiation after laser pre-treatment [1, 9, 51]; Perliatto et al. 2014; [3]. Periolatto et al. [67] suggest potential for design outcomes using stencils to mask UV irradiation on wool, resulting in selective UV exposure on the substrate. Drawing on the digital graphic potential of a CAD controlled laser, Bartlett [9] identified the potential for using an increased dye uptake on synthetic textiles to create imagery, while Akiwowo [3] further developed a laser-based pre-treatment for PET textiles by considering improved dye uptake as an alternative patterning method.

Morgan et al. [54] explored CO₂ laser technology, as an effective surface design tool for wool and wool blends by ascertaining the effect of infrared laser irradiation on the surface and dyeing properties of wool substrates, revealing the potential for textile surface design. The laser technique used laser irradiation to modify the surface of woollen textiles, increasing dye affinity. The process removed microscopic scales from the wool fibre surface, resulting in an enhanced dye performance in the laser-treated areas (Fig. 1).

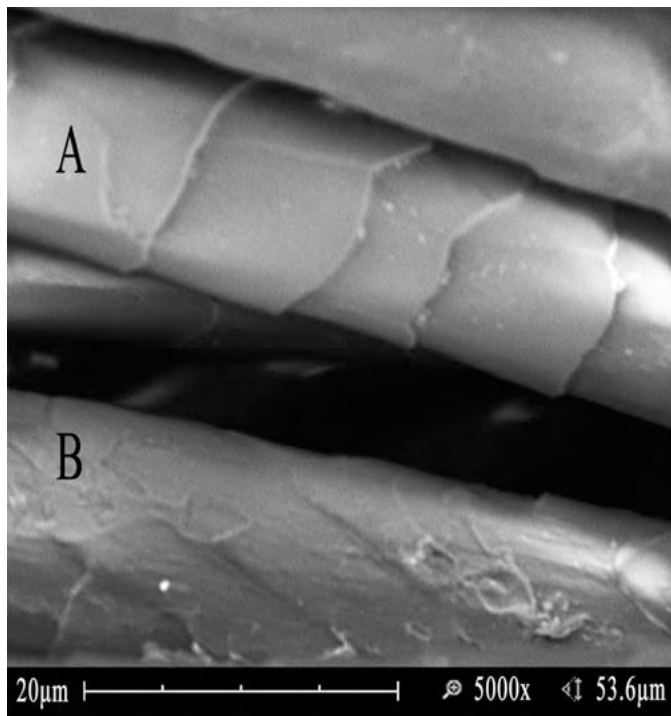


Figure 1 Effect of selective laser irradiation on wool fibres; Wool Fibre A: Wool scales intact. Wool Fibre B: scales have been removed by laser irradiation (Morgan et al, 2014)

Targeted designs were laser marked on the surface of the cloth making use of differential dye uptake to achieve multi-tonal surface design on wool. Laser engraving was found to be effective in removal of the felted or brushed surface fibres of milled wool, to reveal the underlying woven structure. Used in parallel to the dyeing procedures, laser pre-treatment combined three-dimensional relief surfaces with the multi-tonal design effects (Fig. 2).



Figure 2 Laser enhanced dyed and engraved wool samples (Morgan 2016)

Infrared laser irradiation as a pre-treatment to dyeing PET-/wool-blended textiles with reactive and disperse dyes facilitated a novel method of generating multi-coloured textile surface design [51]. Dye exhaustion and colour difference values were calculated, revealing laser irradiation to have a positive effect on the uptake of disperse dye. Microscopic analysis of the laser-irradiated fabric showed an increased PET surface area on the blended textile, causing PET properties to dominate the laser irradiated area. When cross-dyed in a mixed dye bath, the disperse dye was the predominant colour on the laser irradiated areas, while untreated areas retained the reactive dye colour (Fig. 3).



Figure 3 Laser Patterned PET /Wool blend (55/45) design samples dyed with contrasting disperse and reactive dye colours (Morgan 2016)

It was demonstrated that the laser pre-treated wool or blended textiles could be dyed at a reduced temperature and time, saving water and energy while combining colouration and patterning in one process. During colouration, the potential for an estimated 54% reduction of energy was displayed compared to immersion dyeing procedures. Textile performance tests showed that high fastness to washing and rubbing was achieved to meet current industry and consumer standards.

2.2 Laser Colouration and Surface Patterning: Dye Fixation

Existing research studies that utilize laser irradiation for textile colouration and patterning predominantly employ the laser as a pre-treatment to dyeing textiles to enhance the substrate's affinity for dye [3, 9, 21, 36, 49, 54, 76]. However, mechanical tests have shown that the thermal stress of laser irradiation applied to the substrate is ultimately a damaging action (Chow 2012; [7]; therefore, achieving a high depth of shade was detrimental to the tensile strength of the material, revealing scope for improved performance of existing laser dye techniques. In addition, laser pre-treatment techniques used in the creation of surface designs had limitations; only tonal design effects could be achieved. Textile dyeing is an energy-dependent process; therefore, the photothermal properties of infrared laser irradiation present potential to activate a dye reaction on a textile substrate in a targeted manner suitable for the design and patterning of textiles [51]. Attempts toward a laser dye

fixation approach to surface design of textiles can be recognized in a small number of studies. Some success has been reported in introducing dye at the point of laser irradiation [9, 22, 39, 51].

Kearney and Maki reported a system for fixing reactive dye to cotton by way of an argon-ion laser [39] after screen-printing dye onto fabric in the form of a paste. The study provided a feasible low-heat dye-fixation method; however, at a maximum speed of 0.6 mm/s, the process was slow and the screen-printing stage of the process negated the advantage of noncontact laser processing. Textile dyeing company, Zaitex, and Textile equipment company, Tonello, developed a “Garment Flash Printing” system for adding pattern to cotton textile garments using a laser [11] involving a laser, pigments, and a polymeric binder to add colour to cotton fabrics [22]. The process involved the use of a laser to fix the pigment, applied as a resin as an all-over treatment on cotton fabric. Tonello developed the method from a commercial perspective, specifically focusing on application for denim garment finishing.

Bartlett [9] considered the effects of laser irradiating a fabric wet with dye identifying a slight increase in uptake within the dye bath. Morgan [51] further explored the potential of a dye reaction that takes place at the point of laser interaction providing technical refinement of a laser dye-fixation technique and exploration of its creative potential. A laser dye-fixation approach to textile colouration led to the development of the “peri-dyeing” technique. The prefix peri denotes around or adjacent [64]. The peri-dyeing technique considers the laser as a targeted energy source for “on-the-spot” fixation. It involved applying dye locally to the surface of a textile substrate followed by laser irradiation: Therefore, the dye reaction takes place at the point of (or adjacent to) laser interaction with the dye liquor and textile material.

The laser-based peri-dyeing technique [51] allowed intricate, targeted surface design of textile substrates. Photographic quality graphics and multi-coloured surface design effects were achieved on natural wool and synthetic PET and polyamide fabrics. The noncontact laser apparatus allowed precision detail to be achieved on highly textured fabrics or finished three-dimensional garments, providing an advantage over digital printing methods. The permanence and durability of the colouration process were assessed through material performance testing procedures, including fastness to washing, rubbing, and tensile strength, which met with commercial standards across all conducted tests (Morgan et al. 2017c). Peri dyeing enabled digital design innovation, direct-to-garment processing, and potential for customization in the manufacture of finished textile goods with sustainability benefits through reduced energy, water, and chemical consumption [57] (Figs. 4, 5, 6, and 7).



Figure 4 Laser Peri-dyed wool textiles (Morgan 2016)



Figure 5 Laser peri-dyeing on textured and brushed wool fabrics (Morgan 2016)



Figure 6 Peri-Dyed PET textiles: Multicolour and Photographic designs (Morgan 2016)



Figure 7 Direct to garment Peri-Dyed PET sportswear Prototypes (Morgan 2018)

2.3 Laser Surface Texturing: Thermal Setting

Adding surface texture and three-dimensional effects to textiles can provide enhanced functional properties, such as insulation, absorption, compression, or strength in addition to adding shape, movement, and design aesthetics. Three-dimensional surface effects can be added during textile construction, stitching, or via wet techniques such as devoré, flocking, felting, and shibori. Lasers have been used to create design-led three-dimensional forms, such as laser-assisted origami textiles [47], laser-bonded synthetics [24], and laser-moulded textiles by using IR laser irradiation to heat-set predetermined shapes in synthetic textiles (Morgan 2018a).

Laser welding has been used to bond seams in garment construction and in fashion. In the case of thermoplastic fibre fabrics, such as PET, lasers can be used to create stitch-less, water-resistant seams. As reported by The Welding Institute (TWI), this technique often requires an additive that is applied to the seam interface and reacts under the laser energy, melting and bonding the two surfaces together [16]. Current uses of this technology include Airbags, medical and protective clothing, and

footwear with sealed seams. Goldsworthy (2009) explored the design potential of laser welding technology to bond synthetics producing three dimensional and relief qualities. By harnessing the laser for bonding and lamination of the fabrics to produce multi-layered materials, Goldsworthy was able to develop a range of surface finishing methods while keeping the fabric 100% recyclable. Furthering this technique, Paine et al. [65] used laser welding technology to create targeted compressive effect on garments.

Morgan et al. [55] report on a technique for three-dimensional moulding of synthetic textiles using the photothermal properties of infrared laser irradiation. They describe a system to apply and control the three-dimensional effects through controlled tension and targeted laser irradiation. The moulding technique was used to design accurate surface architectures, engineered surface effects, and three-dimensional design features on knitted PET and polyamide textiles (Fig. 8). Combining three-dimensional laser moulding with laser dyeing processes attained an effect akin to shibori dyeing. However, the laser-based technique provided unique design aesthetics, offering control, with a level of precision and repeatability that cannot be achieved with existing shibori processes or textile production techniques.

The use of laser technology to create three-dimensional textile forms presents efficient processing advantages over traditional methods: Unlike regular textile embossing equipment, for each new design, the dry laser process does not require physical moulds or plates to be cast, stitching, or complicated loom set-up, instead, offering ease of pattern change through digital generation of designs. The use of purely synthetic materials may provide additional sustainability benefits for ease of material recovery, redesign, and recycling at end of primary use.



Figure 8 Laser Moulded PET and Polyamide textiles (Morgan 2016)

3 Enzymatic Processing

Enzymes are biocatalysts that catalyse specific chemical reactions within the cells of all living organisms, resulting in the growth and maintenance of the cell. The majority of commercial enzymes are sourced and obtained from a variety of different microorganisms such as bacteria, fungi, and yeast. However, these naturally occurring enzymes are often not found in nature in large quantities and, therefore, require isolating and fermenting for industrial use [61].

Enzymes differ from chemical catalysts in several distinct ways and bring a wide range of processing benefits. Reactions catalysed by enzymes are generally very fast and highly specific, typically performing one type of reaction effectively. Enzymes are capable of catalysing reactions under comparatively mild reaction conditions, such as at temperatures below 80 °C, in atmospheric pressure, and at around neutral pH. In contrast, chemical catalysts often require high temperatures, high pressures, and use of extreme pH. Therefore, enzymes can dramatically reduce energy and chemical consumption and production costs. Enzymes are biodegradable which can help reduce the impact of manufacturing on the environment. Enzymes rarely get involved in side-chain reactions, which eliminate the production of by-products making them extremely efficient during processing unlike typical chemical catalysts which are less specific and often produce unwanted by-products which can prove difficult and costly to dispose of. Furthermore, enzymes are not consumed in reactions and remain unchanged, offering the possibility of repeated and continuous reuse, therefore leading to potentially new sustainable industrial processes such as closed loop [2, 35].

Advances in biotechnology have led to the development and manufacture of new commercial enzymes. These enzymes may have improved properties such as stability under certain conditions, higher activity at lower temperatures, and reduced dependency on additional chemicals (cofactors) being present [61, 66].

Consequently, enzymatic approaches have found a wide range of applications in the textile industry [4, 14, 27, 28, 43], ranging from replacing conventional production methods to novel fabric finishing treatments. Enzymatic desizing is one of the earliest examples of enzymes being implemented on an industrial scale. The enzyme amylase is used in the enzymatic desizing process to break down and remove “size” (starch), a protective lubricant which is commonly applied to yarns during the weaving of fabrics. Since its adoption during the early part of the twentieth century, it has proved to be a valuable method replacing conventional processes which required the use of harsh chemicals such as oxidizing agents [29]. Another group of enzymes called cellulases has found acceptance within textile wet processing. Cellulases are used to bio-polish cotton fabrics, and enzymatic removal of surface microfibrils enables fabrics to maintain a new look for longer. Cellulases and another enzyme group known as laccases are also used in the production of denim fabrics and garments to produce stonewashed looks and/or alter the colour and shade of dyed denim by fading. Stonewashed effects on indigo-dyed cotton denim are used to be created by pumice stones; however, the use of pumice stones caused damage to both fibres and machines. Other well-established enzyme-based textile processes include bio-scouring and bleach clean-up, and both processes are described in more detail in Shen and Smith [80]. Although the value of enzymes in textile processing has long been evident in terms of environmentally friendly, energy and water savings, improved product quality and process integration, and cost reduction, enzymes to date have not been investigated for their creative potential in textile design.

3.1 Protease and Laccase

Research presented within this chapter demonstrates the ability of two specific enzymes, protease and laccase, as creative tools to achieve, through controlled application, innovative colouration and/or decorative surface pattern on textiles.

Protease (EC.3.4.21.62) belongs to a class of enzymes called hydrolases, which are capable of breaking down large molecules into smaller fragments. To date, there has been considerable interest in the application of protease to achieve a variety of functional finishing effects on wool through modification of the wool cuticle scale by catalysing the hydrolysis of peptide bonds in wool protein molecules. Studies have investigated the reduction in wool prickles, improved fibre softness, and anti-shrinkage treatments [78, 79]. However, if not carefully controlled, this group of enzymes can cause significant damage to the wool fibre due to the enzyme penetrating into and attacking the wool fibre core [59, 81], resulting in strength and weight loss [12]. Thus, no commercial treatments have been developed so far, mainly because the use of protease can result in unpredictable, difficult to control reactions leading to unacceptable fibre damage. However, surface modification or controlled degradation of wool fibres through enzymatic treatment presents clear opportunities that could be exploited for aesthetic design purposes.

Laccase (EC.1.10.3.2), belonging to a class of enzymes called oxidoreductase, can catalyse redox reactions, which reduce molecular oxygen to water and simultaneously perform one-electron oxidation of various substrates such as diphenols and aromatic amines with or without a mediator [74, 79].

Laccase products such as DeniLite™ (Novozyme) and PrimaGreen® EcoFade LT100 (Dupont Genencor) based on laccase-mediator systems have found much success as enzymatic processes for decolourizing pre-dyed denim, offering alternatives to traditional abrasive stonewashing processes, where dye is removed from fabrics or garments using pumice stones to achieve colour fading and/or worn effects.






In contrast, laccases are also capable of oxidizing an extensive range of basic aromatic compounds, transforming them into coloured polymeric products via oxidative coupling reactions [46, 74]. The reaction mechanism of laccase catalysation is one electron oxidation of aromatic compounds to form free radicals while reducing molecular oxygen into water. These free radicals are very reactive and then undertake further reactions themselves or with the initial aromatic compound and polymerize in a nonenzymatic pathway to form coloured products. These coloured products are capable of being adsorbed onto or reacting with numerous textile fibres enabling colouration [23, 69, 79]. The potential for laccases to be used within the area of textile colouration, specifically for the generation of decorative surface pattern design, remain relatively unexplored.

3.2 Colouration and Surface Patterning by Enzymatic Degradation

In this study, the enzyme protease was employed to selectively modify a wool/polyester-blended fabric to impart decorative surface patterning [73]. A series of controlled experiments for studying the interaction between enzyme and substrate (a compound on which an enzyme exerts its catalytic effect) were undertaken to achieve either partial or complete removal of the dyed wool fibre component with a view to revealing undyed polyester yarns which formed part of the fabric blend, resulting in novel fading and differential fabric relief (Table 1). Longer treatment times resulted in











greater weight loss and lighter shades being produced, as reflected by K/S values. The activity of protease is highly specific; therefore, it caused neither modification nor damage to the polyester fibres. Investigations concluded that significant subtraction of the dyed wool component from the blend could be achieved if the correct combination of enzyme concentration, agitation, and treatment times were applied.

Table 1. The effect of protease processing at different durations of time on wool degradation from wool/polyester samples dyed using reactive dye Lanazol Blue CE (Source: Prajapati, C).

Wool/polyester fabric samples	Duration of enzymatic treatment with protease (h)				
	Untreated	0.5	1	2	4
Pre-dyed at 2% owf					
<i>K/S</i> (620 nm)	5.89	3.88	2.93	1.40	0.47
Weight loss (%)	-	10.0	16.5	30.0	40.5

In a different study, a laccase-mediator system was explored to generate surface pattern design through selectively decolourizing indigo-dyed cotton fabric [70]. A series of controlled experiments were undertaken, which consisted of enzymatic treatments with different processing parameters using 100% cotton fabric ring-dyed with indigo dye (C.I. Vat Blue 1). Experiments were designed to gain a clear understanding of the interaction between the laccase-mediator system and indigo dye and to achieve partial or complete removal of indigo dye from dyed cotton fibres with a view to revealing undyed cotton fibres and yarns which formed the underlying layers of the fabric. Investigations led to the development of an optimized enzymatic process which enabled indigo-dyed cotton fabrics to be processed to achieve various levels of fading by simply altering processing conditions, as shown in Table 2. Longer treatment times resulted in lighter coloured shades being produced.

Table 2. The effect on dye decolourisation by processing with a laccase-mediator system for different durations of time on cotton (100%) samples ring-dyed with indigo dye (C.I. Vat Blue 1) (Source: Prajapati, C).

Cotton fabric samples	Duration of enzymatic treatment with laccase-mediator system (h)				
	Untreated	0.5	1	2	4
Indigo-dyed with 6-dip and 6-nip					
<i>K/S</i> (640 nm)	19.67	9.40	5.74	5.94	4.11
Indigo dyed with 1-dip and 1-nip					
<i>K/S</i> (640 nm)	6.77	1.92	1.27	0.88	0.61

To explore the decorative pattern design potential of protease and laccase mediator systems, surface-patterning design techniques inspired from traditional Shibori-resist dyeing methods [85] were selected for design trials. Patterns consisting of simple repeats of design elements [86] such as lines or geometric shapes were chosen for exploration to create an all-over repeat pattern across the length of fabric.

Dyed wool/polyester and cotton fabrics comprising different degrees of compression and accessibility were manipulated and prepared using stitching, or folding, pleating, and clamping (as illustrated in Figs. 9, 10, and 11) to achieve surface patterning through enzyme processing. Fabrics were treated in a liquor bath containing the enzymes. In principal, the enzymes would be restricted to selected areas made accessible; therefore, as a result, the enzymes would only be able to degrade or decolourize by fading selected areas of the fabric. This in theory would facilitate the generation of decorative surface patterning through contrast in colour and or texture through the use of localized enzyme treatment.

Results successfully demonstrated a diverse range of highly individual patterns could be generated with the use of varying resist techniques trialled with enzyme processing [70, 73]. The resulting visual aesthetic qualities achieved were heavily governed by the techniques, which controlled the degree of liquor accessibility and penetration, and consequently the level of wool degradation or decolourization. Irregular surface modification resulted in subtle pattern variations and irregularities, and design elements displayed distinctive soft edges. In general, stitch techniques employed (Fig. 10) enabled greater access to the enzyme containing liquor, resulting in lighter and softer coloured patterning. In contrast, pleat, fold, and clamp techniques allowed a different style of patterning; designs with greater colour contrasts and stronger depths of shade result from an increased level of pressure and compression applied with the use of a G-clamp, completely restricting enzyme access to some areas of the fabric (Figs. 9 and 11).

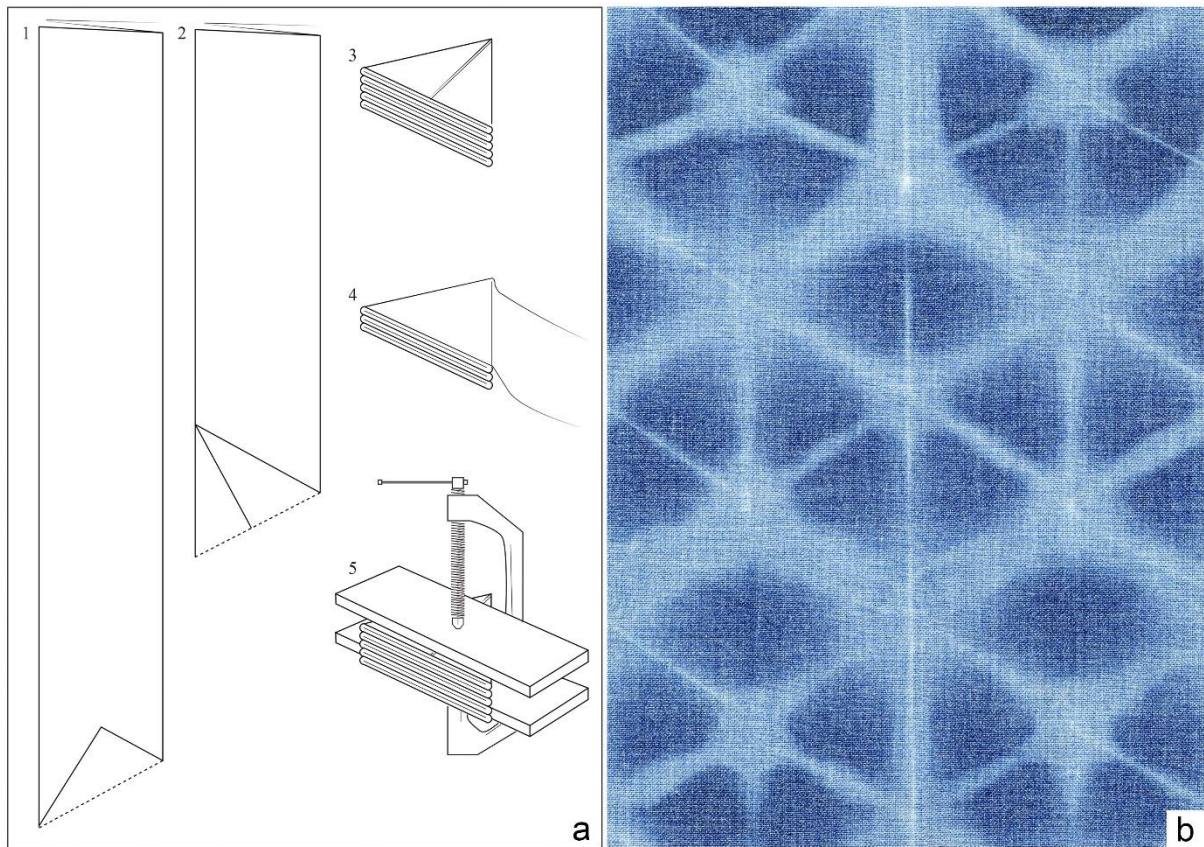


Figure 9. Illustrated diagram showing Shibori technique using pleat, fold and clamp resist method (a) to generate a coloured pattern design using protease processing on wool/polyester blended fabric (b) [73].

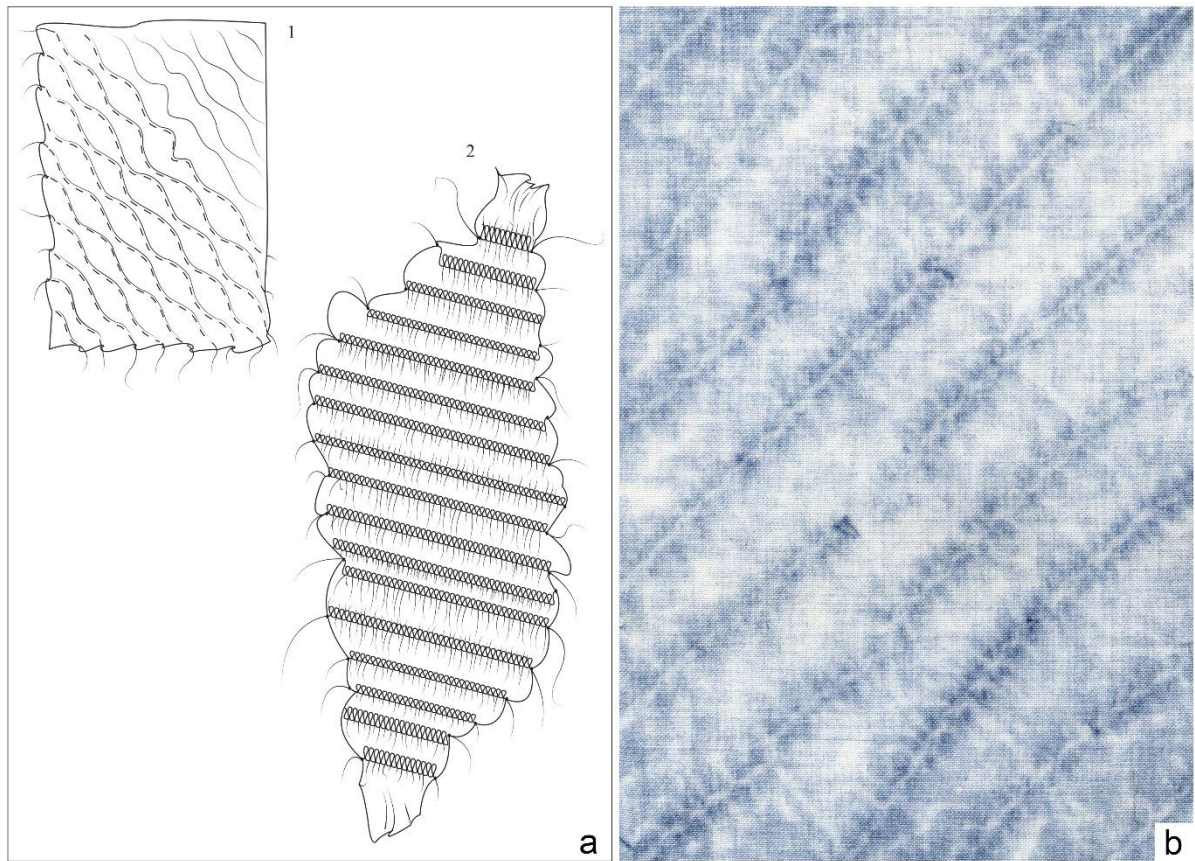


Figure 10. Illustrated diagram showing Shibori technique using stitch resist method (a) to generate a coloured pattern design using protease processing on wool/polyester blended fabric (b) [73].

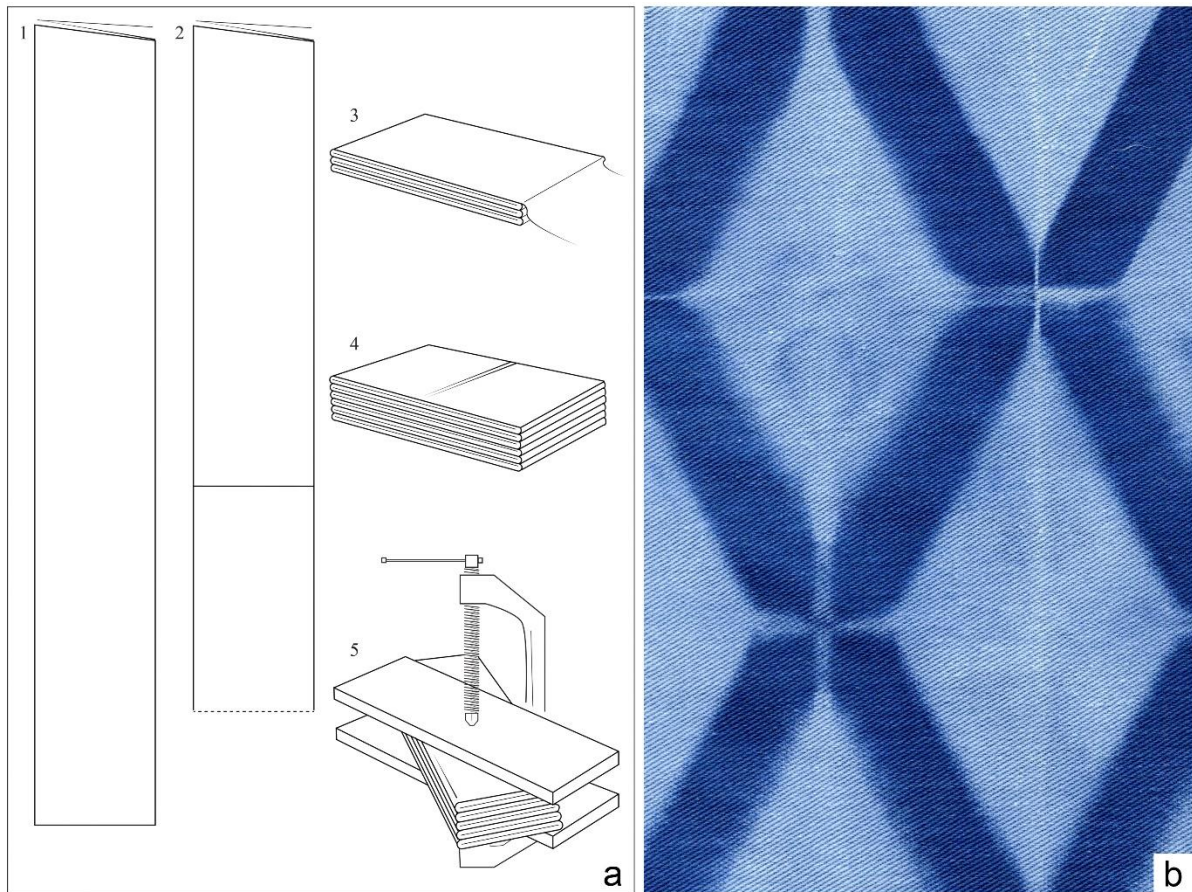






Figure 11. Illustrated diagram showing Shibori technique using pleat, fold and clamp resist method (a) to generate a coloured pattern design using laccase-mediator system on 100% cotton fabric (b) [70].

3.3 Enzymatic Surface Modification for Subsequent Colouration and Surface Patterning





Certain chemicals such as the cationic surfactant cetyltrimethylammonium bromide (CTAB) present on wool fibre can decrease the activity of protease [82, 83]. Therefore, the application of CTAB as a pretreatment was explored as a chemicalresist method to selectively inhibit the activity of protease toward wool fibres to impart decorative patterning. Preliminary studies found that a pretreatment with CTAB followed by enzyme processing was capable of altering wool fibre characteristics enabling differential colouration (dye uptake) and felting properties during subsequent dyeing and postprocessing (Table 3). Fibres treated with CTAB and protease altered the dye uptake and antishrinkage properties. These contrasting properties present opportunities that could be exploited for textile design; however, further work would need to be undertaken to explore its creative potential.

Table 3. The effect on dye uptake of CTAB pre-treated 100% wool fabrics followed by protease treatment and post competitive dyeing using acid dye (Source: Prajapati, C).

C.I. Acid Blue 140	CTAB followed by protease treatment	Protease treatment
Competitively dyed at 0.5 % owf		
Competitively dyed at 5 % owf		

Another enzyme pretreatment method explored the application of protease within a printing paste to selectively modify wool fibre cuticle scales to generate surface pattern. The enzyme was restricted to the surface of the fibre using textile screen-printing methods. Protease applied within an Indulca (a polysaccharide product of gum guar) printing paste led to wool fibre modification through the disruption and removal of wool cuticle scales resulting in greater fibre hydrophilicity, leading to easier dye diffusion especially when dyed at lower temperatures (Table 4). The effects of differential dye uptake in terms of shade depth were explored to produce surface patterning; however, further study is required to produce well-defined surface pattern with this method [70].

Table 4. The effect on dye uptake of protease pre-treated 100% wool fabrics followed by competitive low temperature dyeing using acid dye (Source: Prajapati, C).

Dye	Non-protease treated sample	Protease pre-treated sample
C.I. Acid Blue 140		
C.I. Acid Blue 45		

3.4 Colouration and Surface Patterning by Enzymatic Polymerization

In this study, the potential for laccase to be used within the area of textile colouration, specifically for the generation of decorative surface pattern design, was investigated. A selection of natural phenolic compounds and nonphenolic compounds consisting of naphthalene and benzene derivatives (Table 5) were carefully selected as laccase substrates to synthesize dyes in situ on either nylon 6,6 or wool fabrics.

Table 5. Chemical structures of aromatic compounds selected for study and their corresponding laccase-catalysed coloured solutions and colouration of nylon and wool fabrics. [71]









































Group	Aromatic compound	Chemical structure and form	Coloured product	Coloration on nylon and wool	
1	1,2-Dihydroxybenzene				
	1,4-Dihydroxybenzene				
2	2,7-Dihydroxynaphthalene				
3	Catechin				
4	Ferulic acid				
	Gallic acid				
	Syringic acid				
5	2,5-Diaminobenzenesulfonic acid				
	3-Amino-4-hydroxybenzenesulfonic acid				

Laccase catalysis of the selected aromatic compounds resulted in a variety of colours being produced in aqueous solutions and on both wool and nylon fibres after enzymatic treatment [70]. Each aromatic compound was catalyzed by laccase to form characteristic colour shades, predominately ranging from yellows, oranges, and browns as seen in Table 5. It is believed that the colouration created on both

fibre types was a result of coloured dimeric, oligomeric, and polymeric products formed by laccase oxidation of aromatic substrates, which are capable of reacting non-enzymatically in a nucleophilic manner forming covalent bonds with amino groups found on the surface of nylon and wool fibres [69], to result in reasonable good colour fastness to wash. In general, wool fabric samples were darker in comparison to nylon samples which were lighter and/or brighter. The differences in colouration observed between nylon and wool were due to differences in dyeability characteristics arising from different types and quantities of functional groups present in each fibre (especially amounts of primary amine groups) and aromatic compound structures affecting the various types of molecular interactions occurring between fibre and laccase-synthesized products, in addition to different levels of affinity, rate of uptake, and final saturation values [72].

Prajapati et al. [72] found that a diverse colour palette could be produced with the use of three different aromatic compounds as laccase substrates: 1,4- dihydroxybenzene, 2,7- dihydroxynaphthalene, and 2,5- diaminobenzenesulphonic acid. Various reaction-processing parameters such as buffer systems and pH values, laccase and aromatic compound concentrations, and reaction times were investigated to establish the range of achievable colours, all in the absence of additional chemical auxiliaries. Previously, unreported colours such as blues, greens, and pinks were achieved. The use of varied buffer systems, pH values, and aromatic compound concentrations proved most beneficial for extending the ranges of possible hues. For example, the use of the compound 2,7- dihydroxynaphthalene in the presence of laccase resulted in a variety of hues, ranging from yellow, green, and blue across both fibre types simply through pH control (Table 6).

Table 6. Colour range achieved on wool and nylon when treated with 2,7-dihydroxynapthalene in the presence of laccase using different pH and buffer systems (Source: Prajapati, C).

pH	Wool				Nylon			
	AC	CI	PH	BI	AC	CI	PH	BI
3			-	-			-	-
4				-				-
5				-				-
6				-				-
7				-				-
8	-			-	-			-
9	-	-			-	-		
10	-	-	-		-	-	-	
11	-	-	-		-	-	-	

AC, Acetate buffer; CI, Citrate buffer; PH, Phosphate buffer; BI, Bicarbonate/Carbonate buffer.

To determine the colouration and design potential by laccase catalyzation of the selected aromatic compounds, fabrics were specially constructed using a combination of undyed nylon, wool, and polyester yarns. Basic plain, twill, satin, and sateen structures in addition to simple jacquard weaves were used to generate a selection of woven fabric designs. Weaves were then dyed using the one-step laccasecatalyzed colouration process. As shown in Fig. 12, the use of different fibre types and weave structures enabled simple colour variations to be produced. Shadow, reserve, and contrasting effects are achievable with the newly developed laccase-catalyzed dyeing process.



Figure 12. Examples of one-step laccase-catalysed colouration on nylon, wool, wool/polyester and specially constructed woven jacquard designs, using different dye bath conditions (Source: Prajapati, C).

4 Summary and Conclusions

An overview of the alternative techniques for producing colour, pattern, and surface effects on a range of textiles using laser and enzyme processing is shown in Table 7.

This chapter shows how two different novel approaches, the biological and the digital, can disrupt conventional textile processing each offering potential sustainability benefits within the context of current textile design and manufacture and within emergent and future post-industrial systems of production and consumption.

Selective surface pattern by differential dyeing	<ul style="list-style-type: none">• Laser Coloration and surface patterning: fibre modification• Coloration and surface patterning by enzymatic degradation
Combined three-dimensional and colour finishing	<ul style="list-style-type: none">• Laser Surface texturing: thermal setting• Laser Coloration and surface patterning: fibre modification• Enzymatic surface modification for subsequent coloration and surface
Novel coloration of textile materials	<ul style="list-style-type: none">• Laser Coloration and surface patterning: dye fixation• Coloration and surface patterning by enzymatic polymerisation

Table 7. Overview of alternative techniques for textile colouration, patterning and surface effects

4.1 Key Sustainability Benefits of Laser Processing for Textile Design

The laser-based colouration and design techniques offer innovation with potential sustainability and economic benefits for the field of textiles via eco-efficient manufacture. For example, laser-enhanced dyeing offers potential reductions in energy and wastewater effluent through reduced dyeing temperatures and improved dye performance. Low-temperature processing reduces overall dyeing time and temperature from standard practice, displaying potential for an estimated 54% reduction of energy during dye production in the case of the laser pre-treated and dyed wool [54]. The ability to reduce energy used in dyeing by over half would offer exceptional savings with both economic and environmental benefits. Some loss in tensile strength was apparent after laser irradiation, and despite enhancing the affinity for dye, the process did not altogether omit immersion dyeing procedures. These issues were addressed via the laser peri-dyeing technique [51], which added additional water, energy, and chemical saving benefits, further reducing the water and dye required for colouration of wool and synthetic substrates by elimination of dye baths used in conventional exhaust dyeing procedures, while retaining permanence and durability. Laser moulding [55] described a dry and efficient process that does not require additional materials, such as thread for stitching. Therefore, using the technique for surface design effects could eliminate the need for additional wet finishing or embellishment for decorative and functional textiles.

Combining the functionality of the laser to perform multiple production tasks at once, such as pattern cutting or laser engraving milled wool as well as the laser dyeing techniques, would allow additional environmentally sustainable benefits to the process compared to outsourcing each individual stage of the production process in addition to storage and transport between phases. Combining techniques in one stage has potential to offer fast response in today's fast changing market, with easily changed CAD files allowing smaller product runs than financially permitted by exposing individual screens for screen printing or die cutters for product pattern cutting. Therefore, as well offering sustainability through reduced temperatures and improved dye performance, laser technology could offer additional advantages through a potential change in production systems.

The flexibility and immediacy of digital processing benefit short-run production, textile sampling, and garment prototyping compared to conventional textile processing techniques that are aimed to be cost-effective for bulk manufacture. Processing limitations of laser techniques may include restrictions in size of the laser bed area, or processing speed for bulk and large volume manufacture. Similar to digital textile printing, turn-around times may be slower than that of rotary or screen printing methods when volumes increase. However, garment and textile specific multi-head laser machinery capable of direct-to-garment (DTG) finishing and processing of continuous fabric lengths have already been commercialized for the denim industry [34], showing that application-specific laser machinery can be engineered to overcome size and speed constraints for emerging laser textile processing techniques.

The laser-based design techniques discussed in this chapter are capable of digital design generation and targeted, direct-to-garment processing on textile or garment "blanks," postconstruction. Further research involving partners from four sectors of the textile industry [56] identified commercial viability and the opportunity for these digital laser processes to move the design stage further down the production cycle to allow for late-stage decisions and design flexibility, providing a responsive approach to design and distributed manufacture. Providing the textile industry with responsive or agile manufacturing opportunities such as these may offer reduced lead times and smaller minimum orders to reduce surplus stock and minimize or eliminate the creation of excess waste of textile goods; in addition, they may facilitate bespoke or customized production opportunities.

4.2 Key Sustainability Benefits of Enzymatic Processing for Textile Design

Studies discussed in Sect. 3.2 demonstrated the ability of protease and laccase as creative design tools for colouration and surface patterning by enzymatic degradation. With both studies, effects similar to those achieved with conventional surface design processes such as *devoré* ("burnt out") and discharge printing were achieved. Both patterning styles have remained popular and significant since first introduced because the effects obtained from these processes are often different and aesthetically superior to direct screen-printing styles [48] and digital textile printing. Although both processes are simple and inexpensive methods for producing patterned fabrics through the application of a chemical paste, the processing pastes require the use of either strong alkalis such as sodium hydroxide or reducing agents, in addition to chemical auxiliaries [73]. The heavy use of these compounds can be toxic and hazardous to handle and generate effluents that are difficult to treat and damaging toward the environment [41, 45].

In contrast, surface patterning through enzymatic hydrolysis with protease or decolourization with laccase-mediator system offers simpler, cleaner, and safer alternative processing methods, which principally eliminate or reduce the use of conventional reducing and/or oxidizing agents, chemical

auxiliaries, and elevated temperatures for processing. The precise reaction specificity of enzymatic processes facilitates specific and targeted textile finishing without causing undesirable effects such as deteriorating fabric qualities and causing damage to other components. In addition, both enzymatic processes offer new unique design aesthetics which enable the production of individual nonidentical, but corresponding surface design patterns with subtle variations, irregularities, and unique characteristics which would be difficult to reproduce and replicate by the means of conventional textile processes. Currently, there is considerable interest within the textile industry to create fabrics with artisan aesthetics, and these qualities are understood to be positive in the current industry where consumers regularly seek individual and unique pieces.

Conventional dyeing processes generally involve the use of different chemicals and dyeing auxiliaries in addition to high temperatures to assist the dyeing process. The colouration of wool and nylon can be achieved with the use of several dye classes, the most important of which are acid, mordant, and premetallized dyes, all of which are applied under acidic conditions with the use of high temperatures, generally at the boil [13, 44]. Colouration and surface patterning by enzymatic polymerization discussed in Sect. 3.4 present advantages over conventional dyeing methods, principally the elimination of premanufactured dyes and chemical auxiliaries, and dyeing at ambient temperatures, therefore reducing energy use, the complexity of the dyeing process, and downstream processing, leading to possible economic and environmental advantages. Although the study shows that a good range of colours is achievable by this method, it is not known yet whether a full gamut of colour shades can be achievable. The enzymatic dyeing process offers opportunities for multiple colours and shading to be achieved through simple alterations in processing conditions, which is currently not possible with conventional dyes and methods. The results also demonstrate the ability of laccase as a novel creative tool, which permits effective surface patterning through controlled application for shadow and contrast coloured effects.

The opportunities discussed could provide the textile industry with realistic and viable options to use enzyme-based colouration and surface patterning processes; however, further study is required to examine whether the enzymatic processes have the potential to be scaled up to a viable industrial process which can be reproducible and meet commercial standards.

Note

This work was undertaken through the LEBIOTEX project (Laser Enhanced Biotechnology for Textile Design) – a collaborative research venture between De Montfort University and Loughborough University in the UK. The project was led by Professor Jinsong Shen (De Montfort University) and Dr. Faith Kane (now at Massey University, NZ) with consultation from Professor John Tyrer (Loughborough University, UK) and Dr. Edward Smith (De Montfort University, UK), and research work undertaken by Dr. Laura Morgan (now at University of the West of England) and Dr. Chetna Prajapati (now at Loughborough University). The initial project ran from 2012 to 2015 and explored new opportunities for sustainable textile colouration and surface design using enzyme and laser technologies. The project was funded by the Arts and Humanities Research Council (AH/J002666/1) and was supported by industrial project partners Camira Fabrics, Speedo, and Teresa Green Design. More information about the work can be found here: <https://www.dmu.ac.uk/research/research-faculties-and-institutes/art-design-humanities/team/innovativetechnologies-for-textile-colouration-and-surface-design/innovative-technologyfor-textile-colouration-and-surface-design.aspx>

References

1. Addrison J (2009) Jenny Addrison. [online] Cutting edge: laser and creativity symposium, Loughborough University, School of the Arts, 2009. Available from: <http://www.cuttingedgesymposium.com/pdf/jenny-addrison.pdf>. Accessed 30 Sept 2012
2. Aehle W (ed) (2007) Enzymes in industry, production and applications. Wiley-VCH Verlag GmbH & Co, Weinheim, pp 99–262
3. Akiwowo K (2015) Digital laser-dyeing: colouration and patterning techniques for polyester textiles. Thesis (PhD), Loughborough University
4. Araújo R, Casal M, Cavaco-Paulo A (2008) Application of enzymes for textile fibres processing. *Biocatal Biotransformation* 26(5):332–349
5. Atav R (2013) The use of new technologies in dyeing of proteinous fibres. In: Gunay M (ed) Eco-friendly textile dyeing and finishing. Intech, Rijeka
6. Bahnert T (1995) Excimer laser irradiation of synthetic fibres as a new process for the surface modification of textiles - a review. *Opt Quant Electron* 27(12):1337–1348
7. Bahtiyari MI (2011) Laser modification of polyamide fabrics. *Opt Laser Technol* 43(1):114–118
8. Banchero M (2013) Supercritical fluid dyeing of synthetic and natural textiles – a review. *Colour Technol* 129(1):2–17
9. Bartlett SN (2006) Lasers and textiles: an exploration into laser dye-fibre interaction and the process of technology transfer. Thesis (PhD), Loughborough University
10. Berkmanns DJ, Faerber DM (2010) Laser basics, laserline technical. Boc, The Linde Group, Surrey
11. Billian (2015) Tonello presents multicolour laser. [online] Textile World. Available from http://www.textileworld.com/articles/2015/march/tonello_presents_multicolour_laser. Accessed 30 Sept 2015
12. Bishop DP, Shen J, Heine E, Hollfelder B (1998) The use of proteolytic enzymes to reduce wool fibre stiffness and prickly. *J Text Inst* 89:546–553
13. Broadbent AD (2001) Basic principles of textile colouration. Bradford, Society of Dyers and Colourists
14. Cavaco-Paulo A, Gübitz G (2003) Catalysis and processing. In: Cavaco-Paulo A, Gübitz GM (eds) Textile processing with enzymes. Woodhead Publishing Ltd, Cambridge, pp 86–119
15. Chow YL, Chan CK, Kan CW (2011) Effect of CO₂ laser treatment on cotton surface. *Cellulose* 18(6):1635–1641
16. Clearweld (2012) Laser welding of thermoplastic textiles. Clearweld, New York
17. Cornforth M (2019) Water and chemical free dyeing with CO₂, World Textile Information Network. Available from <https://www.wtin.com/article/2019/march/250319/water-and-chemical-free-dyeing-with-co2/?freeviewlinkid=99512>. Accessed 24 July 2019

18. Costin DJ, Martin HM (1999) System and method for processing surfaces by a laser. [Patent] US005916461a, Perrysburg: Ohio
19. Coulter J (2018) The designers leap: boundary jumping to foster interdisciplinarity between textile design and science. *J Text Design Res Pract* 6(2):137–162. <https://doi.org/10.1080/20511787.2018.1451211>
20. Czyzewski, A. (2012) Fruits of the loom. *The Engineer*, July 2012
21. Esteves F, Alonso H (2007) Effect of CO₂ laser radiation on surface and dyeing properties of synthetic fibres. *Res J Text Appar* 11(3):42–47
22. Fall, T. (2015) Printing by laser. *International Dyer* (3) p 35
23. Fu J, Nyanhongo GS, Gübitz GM, Cavaco-Paulo A, Kim S (2012) Enzymatic colouration with laccase and peroxidases: recent progress. *Biocatal Biotransformation* 30(1):125–140
24. Goldsworthy K (2014) Design for cyclability: proactive approaches for maximising material recovery. *Making Futures Journal* 3:249
25. Goldsworthy K, Ross S, Peters G (2016) Towards a quantified design process: bridging design and life cycle assessment. In: *Proceedings of circular transitions*, Chelsea College of Arts and Tate Britain, London, 23–24 Nov 2016
26. Hare M (2018) Introducing: IndiDye by expert Fibres, The Ultrasonic Plant Dye Revolution. <https://sourcebook.eu/en/blog/introducing-indidye-expert-fibres>. Accessed 16 Oct 2019
27. Heine E, Höcker H (1995) Enzyme treatments for wool and cotton. *Rev Prog Colour Relat Top* 25:57–63
28. Heine E, Höcker H (2001) Bioprocessing for smart textiles and clothing. In: Tao X (ed) *Smart fibres, fabrics and clothing*. Woodhead Publishing Ltd, Cambridge, pp 254–263
29. Hickman WS (1995) Preparation. In: Shore J (ed) *Cellulosics dyeing*. Society of Dyers and Colourists, Bradford, pp 81–151
30. Hitz CB, Ewing JJ, Hecht J, Hitz CB (2001) *Introduction to laser technology*. Wiley, New York
31. Hua L, Shaoliua H, Youqing W, Bo L, Jin Z (2002) Polymer surface modification with lasers. In: *Proc SPIE* 4644
32. Hur E (2010) *Nomadic Wonderland*. [online] Ensuk Hur. Available from <http://www.eunsukhur.com/>. Accessed Sept 2012
33. Indidye® (n.d.) Merging ancient dyes with innovation. <http://www.indidye.com/technology/>. Accessed 23 July 2019
34. Jeanologia (2015) Jeanologia Press Dossier. [online] Jeanologia. Available from <http://jeanologia.com>. Accessed 30 Jan 2016
35. Jenkins RO (2003) Enzymes. In: Cavaco-Paulo A, Gübitz GM (eds) *Textile processing with enzymes*. Woodhead Publishing Ltd, Cambridge, pp 1–40

36. Kan CW (2008) Effects of laser irradiation on polyester textile properties. *J Appl Polym Sci* 107(3):1584–1589
37. Kan CW (2014) A novel treatment for textiles: plasma treatment as sustainable technology. CRC Press, Boca Raton
38. Kan CW, Yuen CWM, Cheng CW (2010) Technical study of the effect of CO₂ laser surface engraving on the colour properties of denim fabric. *Colour Technol* 126(6):365–371
39. Kearney K, Maki A (1994) Using laser technology to apply fibre reactive dye on cotton. *Text Chem Colour* 26(1):24–28
40. Knittel D, Schollmeyer E (1998) Surface structuring of synthetic fibres by UV laser irradiation. *Polym Int* 45(1):103–117
41. Lacasse K, Baumann W (2012) Textile chemicals: environmental data and facts. Springer-Verlag Berlin Heidelberg, Germany
42. Lakshmanan SO, Raghavendran G (2017) Low water-consumption technologies for textile production. In: Senthilkannan Muthu S (ed) *Sustainable fibres and textiles*. Woodhead Publishing, Cambridge
43. Lenting HBM (2007) Industrial enzymes. In: Aehle W (ed) *Enzymes in industry: production and applications*. Wiley-VCH Verlag GmbH & Co, Weinheim, pp 99–262
44. Lewis DM (1992) *Wool dyeing*. Society of Dyers and Colourists, Bradford
45. Makarov SV, Mundoma C, Svarovsky SA, Shi X, Gannet PM, Simoyi RH (1999) Reactive oxygen species in the aerobic decomposition of sodium hydroxymethanesulfinate. *Arch Biochem Biophys* 367:289–296
46. Mate DM, Alcalde M (2015) Laccase engineering: from rational design to directed evolution. *Biotechnol Adv* 33:25–40
47. Matthews J (2011) *Textiles in three dimensions: an investigation into processes employing laser technology to form design-led three-dimensional textiles*. Thesis (PhD), Loughborough University
48. Miles LWC (1994) *Textile printing*. Society of Dyers and Colourists, Bradford
49. Montazer M, Javad S, Harifi T (2011) Effect of CO₂ irradiation on various properties of polyester fabric: focus on dyeing. *J Appl Polym Sci* 124(1):342–348
50. Montazer M, Chizarifardb G, Harifia T (2013) CO₂ laser irradiation of raw and bleached cotton fabrics, with focus on water and dye absorbency. *Colour Technol* 130:13–20
51. Morgan L (2016) *Laser textile design: the development of laser dyeing and laser moulding processes to support sustainable design and manufacture*. Doctoral Thesis, Loughborough University
52. Morgan L (2017) Interdisciplinary textile design research for material innovation: synthesising design, science and industry collaboration. In: *Intersections: collaboration in textile design research conference*, Loughborough University, London, UK, 13 Sept 2017

53. Morgan L, Matthews J (2018) Intersections: collaborations in textile design research. *J Text Design Res Pract* 5(2):Intersections Special Issue). <https://doi.org/10.1080/20511787.2017.1484048>
54. Morgan L, Tyrer J, Kane F (2014) The effect of CO₂ laser irradiation on surface and dyeing properties of wool for textile design. In: Proceedings of the international congress on applications of lasers and electro-optics (ICALEO), San Diego, 19–23 Oct 2014
55. Morgan, L., Kane, F., Shen, J., Tyrer, J. (2018a) Laser shibori: a digital moulding technique supporting sustainable textile design in three dimensions. *J Text Design Res Pract* 6 (1):Circular Transitions Special Issue. <https://doi.org/10.1080/20511787.2018.1493836>
56. Morgan L, Shen J, Matthews J, Tyrer J (2018b) Laser peri-dyeing for agile textile design: implementing laser processing research within the textile industry. In: Proceedings of AUTEX world textile conference, Istanbul, 20–22 June 2018
57. Morgan L, Kane F, Tyrer J, Shen J (2019) Textile led sustainable innovation of colouration and patterning for sportswear. In: Gwilt A, Ruthschilling E, Payne A (eds) *Global perspectives on sustainable fashion*. Bloomsbury, London
58. Moriarty L (2004) Laser cut rubber lace panels. [online] Lauren Moriarty. Available from <http://www.laurenmoriarty.co.uk/>. Accessed 10 Sept 2012
59. Nolte H, Bishop DP, Höcker H (1996) Effects of proteolytic and lipolytic enzymes on untreated and shrink-resist treated wool. *J Text Inst* 87:212–226
60. Nourbakhsh S, Ebrahimi I, Valipour P (2011) Laser treatment of the wool fabric for felting shrinkage control. *Fibres and Polymers* 12(4):521–527
61. Novozymes A/S (2013) *Enzymes at work*, 4th edn. Novozymes, Bagsvaerd
62. Ondogan Z, Pamuk O, Ondogan EN, Ozguney A (2005) Improving the appearance of all textile products from clothing to home textile using laser technology. *Opt Laser Technol* 37(8):631–637
63. Ortiz-Morales M, Poterasu M, Acosta-Ortiz SE, Compean I, Hernandez- Alvarado MR (2003) A comparison between characteristics of various laser-based denim fading processes. *Opt Lasers Eng* 39(1):15–24
64. Oxford (2014) *Oxford English dictionary*. Oxford University Press, Oxford
65. Paine H, Goldsworthy K, Baurley S (2017) Evolutionary approach of a textile designer through cross-disciplinary research practice: a case study in the field of advanced methods for joining textiles. In: Proceedings of intersections: collaborations in textile design research conference, Loughborough University, London, UK, 13 Sept 2017
66. Peplow M (2015) The enzyme hunters. [WWW] Chemistry World, The Royal Society of Chemistry. Available from <https://www.chemistryworld.com/feature/the-enzyme-hunters/> 8306.article. Accessed 15 Aug 2019
67. Periolatto M, Ferrero F, Migliavacca G (2014) Low temperature dyeing of wool fabric by acid dye after UV irradiation. *J Text Inst* 105(10):1058–1064

68. Philpott R, Kane F (2016) Textile Thinking: a flexible, connective strategy for concept generation and problem solving in interdisciplinary contexts. In: Marchand THJ (ed) Craft work as problem solving – ethnographic studies in design and making. Ashgate, Farnham
69. Polak J, Jarosz-Wilkolazka A (2012) Fungal laccases as green catalysts for dye synthesis. *Process Biotechnol* 47:1295–1307
70. Prajapati CD (2016) Biotechnology for textile colouration and surface pattern. PhD, De Montfort University, UK
71. Prajapati CD, Smith E, Kane F, Shen J (2017) Enzyme catalysed colouration and surface patterning. *Int Dyers* 202(3):59–61
72. Prajapati CD, Smith E, Kane F, Shen J (2018) Laccase-catalysed colouration of wool and nylon. *Colour Technol* 134:423–439
73. Prajapati CD, Smith E, Kane F, Shen J (2019) Selective enzymatic modification of wool/polyester blended fabrics for surface patterning. *J Clean Prod* 211:909–921
74. Riva S (2006) Laccase: blue enzymes for green chemistry. *Trends Biotechnol* 24(5):219–226
75. Sandu I, Vrinceanu N, Comapp D (2009) Study of surface modifications of wool fabrics by UV excimer laser irradiation treatment. *Rev Chim* 60(9):944–948
76. Shahidi S, Moazzenchi B, Ghoranneviss M (2013) Improving the dyeability of polypropylene fabrics using laser technology. *J Text Inst* 104(10):1113–1117
77. Shaikh A (2009) Water conservation in textile industry. *Pak Text J* 58:48–51
78. Shen J (2009) Enzyme application in wool finishing. In: Johnson NAG, Russell IM (eds) *Advances in wool technology*. Woodhead Publishing Ltd, Cambridge, pp 167–182
79. Shen J (2019) Enzymatic treatment of wool and silk fibres. In: Cavaco-Paulo A, Nierstrasz VA, Wang Q (eds) *Advances in textile biotechnology*. Woodhead Publishing Ltd, Cambridge, pp 77–105
80. Shen J, Smith E (2015) Enzymatic treatments for sustainable textile processing. In: Blackburn RS (ed) *Sustainable apparel, production, processing and recycling*. Woodhead Publishing, Cambridge, pp 119–133
81. Shen J, Bishop DP, Heine E, Hollfelder B (1999) Some factors affecting the control of proteolytic enzyme reaction on wool. *J Text Inst* 90:404–411
82. Smith E, Shen J (2012) Enzymatic treatment of wool pre-treated with cetyltrimethylammonium bromide to achieve machine washability. *Biocatal Biotransformation* 30(1):38–47
83. Smith E, Farrand B, Shen J (2010) The removal of lipid from the surface of wool to promote the subsequent enzymatic process with modified protease for wool shrink-resistance. *Biocatalysis Biotransformation* 28(5–6):329–338
84. Spoonflower (n.d.) How does it work? https://www.spoonflower.com/how_it_works. Accessed 16 Oct 2019.

85. Wada Y, Rice M, Barton J (2012) Shibori: the inventive art of Japanese shaped resist dyeing. Kodansha International, Tokyo
86. Wells K (2000) Fabric dyeing & printing. Conran Octopus Limited, London
87. Wong W, Chan K, Yeung KW, Lau K (2003) Surface structuring of poly(ethylene terephthalate) by UV excimer laser. J Mater Process Technol 132(1–3):114–118
88. Wong W, Chan K, Yeung KW, Lau KS (2007) A potential textile application of UV excimer laser irradiation on polyester fabrics. Res J Text Appar 3(2):1–6
89. Xin JH, Zhu R, Hua J, Shen J (2002) Surface modification and low temperature dyeing of wool treated by UV radiation. Colour Technol 118(4):169–173